

NASKAH PUBLIKASI (*MANUSCRIPT*)

**PENGARUH LAMA PERENDAMAN SERAT PADA LARUTAN ALKALI
TERHADAP KEKUATAN MEKANIK KOMPOSIT SERAT TANDAN
KOSONG KELAPA SAWIT**

***EFFECT OF FIBER IMMERSION TIME ON ALKALINE TREATMENT
TO THE MECHANICAL STRENGTH OF THE COMPOSITE
REINFORCED OIL PALM EMPTY FRUIT BUNCHES (OPEFB) FIBERS***

Febri Adyatama¹, Agus Mujianto²



**FEBRI ADYATAMA
NIM. 1911102442006**

**DOSEN PEMBIMBING:
AGUS MUJIANTO, S. T., M. T**

**PROGRAM STUDI S1 TEKNIK MESIN
FAKULTAS SAINS DAN TEKNOLOGI
UNIVERSITAS MUHAMMADIYAH KALIMANTAN TIMUR
SAMARINDA
2023**

Naskah Publikasi (*Manuscript*)

Pengaruh Lama Perendaman Serat pada Larutan Alkali terhadap Kekuatan Mekanik Komposit Serat Tandan Kosong Kelapa Sawit

Effect of Fiber Immersion Time on Alkaline Treatment to the Mechanical Strength of the Composite Reinforced Oil Palm Empty Fruit Bunches (OPEFB) Fibers

Febri Adyatama¹, Agus Mujianto²



Febri Adyatama
NIM. 1911102442006

Dosen Pembimbing:
Agus Mujianto, S. T., M. T

PROGRAM STUDI S1 TEKNIK MESIN
FAKULTAS SAINS DAN TEKNOLOGI
UNIVERSITAS MUHAMMADIYAH KALIMANTAN TIMUR
SAMARINDA
2023

HALAMAN PENGESAHAN

**PENGARUH LAMA PERENDAMAN SERAT PADA LARUTAN ALKALI
TERHADAP KEKUATAN MEKANIK KOMPOSIT SERAT TANDAN
KOSONG KELAPA SAWIT**

NASKAH PUBLIKASI

Disusun oleh:

Febri Advatama
NIM. 1911102442006


Disetujui oleh:
Pada Tanggal 06 Januari 2023

Penguji 1




Hery Tri Waloyo, S. T., M. T
NIDN. 1107108702

Penguji 2

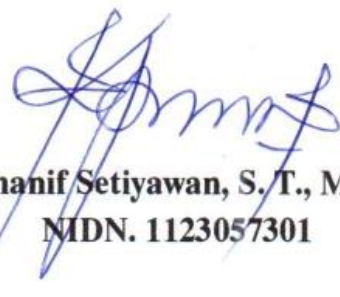

Khanif Setiyawan, S. T., M. T
NIDN. 1123057301

Mengetahui,
Ketua Prodi S1 Teknik Mesin

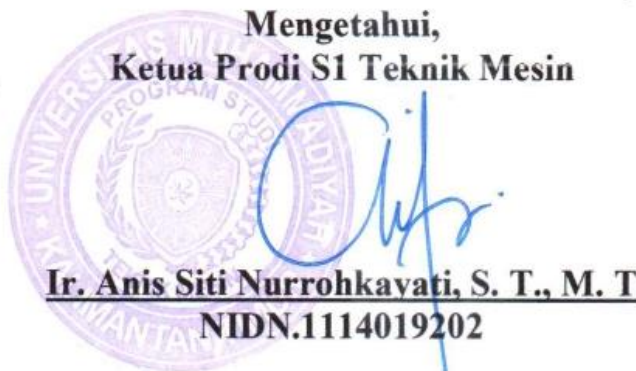

Ir. Anis Siti Nurrohkayati, S. T., M. T
NIDN.1114019202

Effect of Fiber Immersion Time on Alkaline Treatment to the Mechanical Strength of the Composite Reinforced Oil Palm Empty Fruit Bunches (OPEFB) Fibers

Agus Mujianto^{1, a)}, Asslia Johar Latipah^{2, b)}, Hery Tri Waloyo^{1, c)}, and Febry Adytama^{1, d)}

¹*Mechanical engineering department of Muhammadiyah Kalimantan Timur University, Kalimantan Timur, Indonesia*

²*Informatic engineering of Muhammadiyah Kalimantan Timur University, Kalimantan Timur, Indonesia*

Author Emails

^{a)} am713@umkt.ac.id, ^{b)} ajl722@umkt.ac.id, ^{c)} htw182@umkt.ac.id, ^{d)} 1911102442006@umkt.ac.id

Abstract. The more outstanding palm oil production, the greater the waste production. one of them is the fiber of empty palm oil fruit bunches (EPOFB). The use of empty palm fiber bunches is still only in the agricultural sector. In other places, the development of natural fiber composite is currently being developed. This encourages the better utilization of empty palm oil fruit bunches (EPOFB) as a reinforcement for composites. One of the weaknesses of natural fibers as reinforcement in composites is the hydrophobicity of natural fibers, so the ability to bind the matrix to natural fibers is low. One way to overcome this is by immersion in an alkaline solution. The results of immersion in alkaline solutions also depend on the immersion time. Therefore, this research will see how the immersion time affects the composite's mechanical strength. This research is essential to find out the right time for immersion in an alkaline solution to optimize production time. Immersion was done for 2 hours, 4 hours, and 6 hours. The test results have shown that the immersion times affect the material's mechanical strength. There was an increase in strength from immersion 2 hours to 6 hours.

Keyword: Empty Fruit Bunches, composite, immersion time, alkaline treatment

INTRODUCTION

The palm oil business is expanding at a rapid rate in the modern era, which has led to a corresponding increase in waste production. Waste products from the oil farming sector, including used palm oil bunches, palm fiber, and sludge. While some progress is made in the empty oil palm fruit bunches as road paving and fertilizer, the rest simply become waste that is very distressing to the neighborhood. In particular, the fiber from these empty palm oil bunches has potential as a composite reinforcement material. Combining natural materials into composites improves the material in several ways, including its resistance to corrosion, its aesthetic appeal, and the smoothness of its surface. Recently, researchers have paid little attention to the potential of empty oil palm bunches as composite reinforcement. Therefore, it is essential to investigate empty palm fruit bunch fiber as a composite reinforcing material to find solutions to environmental issues and develop new materials. The mechanical strength of composites reinforced by empty palm fruit bunches is analyzed, with a focus on the impact of variations in immersion during fiber preparation.

Natural fiber necessitates a process of cleaning because it is frequently contaminated. Several researches have reported on the mechanism of fiber preparation treatment for natural fiber materials. Increasing the mechanical strength of the composite through alkali treatment of acacia arabica and kenaf fibers has been shown to be effective

[1, 2]. The lignin in fiber from empty palm oil bunches can be removed by alkali treatment, resulting in a stronger bond with the matrix [3]. The next challenge is figuring out how to strengthen the connection between the fiber and the epoxy (matrix). The literature reveals that chemical treatment can enhance the composite by promoting greater fiber-to-matrix adhesion. The most common treatment for fibers is an alkaline by using sodium hydroxide (NaOH) [4]. The results of flexural strength tests on sugarcane fiber composites show that the strength of the material improves the longer the fibers are submerged in alkaline solutions [5, 6]. Thistle fiber and napier fiber investigations revealed findings similar with those from sugar cane fiber study [7, 8]. Extensive contact with an alkaline solution causes the surface fiber to roughen, resulting in a stronger connection with the matrix [9]. The fiber of empty palm oil bunches is likewise a natural fiber, thus if it is utilized as reinforcement in composites without treatment, the bond between the reinforcement and the matrix is weak. Consequently, studies on the alkaline treatment of empty oil palm fruit bunches are required. The purpose of this study was to compare the flexural strength of the composite fiber of empty palm oil fruit bunches to the mechanical test results after soaking the fibers in an alkaline solution (NaOH) for various lengths of time.

METHOD AND MATERIALS

Research to obtain data on the effect of using variations in the soaking time of empty palm oil fruit bunches was carried out using palm fiber which had undergone a process of separating the seeds and bunches. The fiber of empty palm fruit bunches has a density of 0.47 g with a tensile strength of 10008 kg [10]. Before being used as a composite reinforcement, the fiber is soaked in an alkaline solution. The alkaline solution used is NaOH. The fiber is soaked in the liquid with different duration 2, 4, and 6 hours. After being soaked, the fibers are cleaned in running water and then dried in the sun to dry. Figure 1 shows the soaking and drying process. Figure 1(a) shows a row of jerry cans used for the process of soaking bunch fiber using NaOH solution. The fiber drying process is done using natural drying under the sun as shown in figure 1 (b). In this research, resin polyester was used as matrix

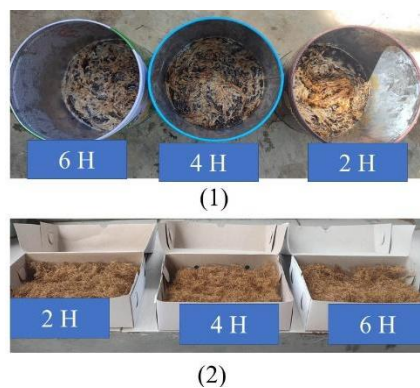


FIGURE 1. Natural fiber pre-processing (1) fiber immersed in an alkaline (2) The fibers are dried in the sun to dry.

The manufacturing procedure for producing natural fiber composites is carried out using the hand lay up method. The ratio of the volume of the matrix to the volume of its reinforcement or OPEFB fiber is 80%:20%. Each material is calculated as its mass with the standard density of the material. Natural fibers are prepared by applying pressure to facilitate fabrication as shown in Figure 2. After printing, the composite is left for five hours and then unloaded from the mold.



FIGURE 2. hand layup process

In this study, mechanical studies were carried out to determine the performance of the composite by bending and tensile testing. Flexure strength is the greatest strength that can be received due to external loading. As a result of the flexure test, the upper part is stressed, while the lower part will experience tensile stress; in composite materials, the compressive strength will be higher than the tensile strength because it cannot withstand the tensile stress received, and the specimen will break. In this study, using the ASTM D7264 standard flexure test. The tensile test is to determine the tensile strength and strain values of the matrix or fiber composites. The method used is that the object being tested is clamped in the testing machine, with the load slowly increasing until a certain load, and in the end, the object being tested breaks. The tensile load acting on the object under test will increase in length and, at the same time, decrease the diameter of the object being tested. This test used the ASTM D3039 standard.

RESULT AND DISCUSSION

Flexure Strength

The bending test is carried out after waiting for the composite to dry completely. Test samples are produced from the fabrication process using larger molds so that at a single process can produce several samples. Tests were carried out using the UTM test machine with settings in accordance with ASTM standards. The results of the flexure test from this study are figure 3.

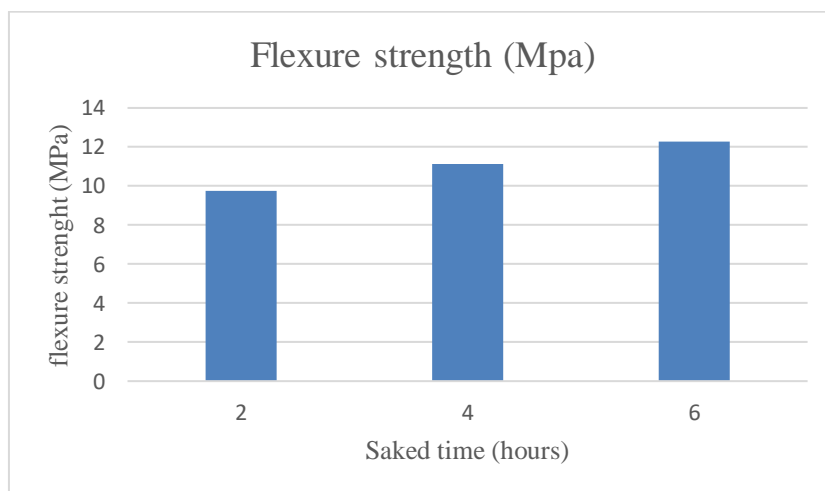


FIGURE 3. flexure strength of composite reinforcement OPEFB fiber

Figure 3 shows the bending strength of the immersion composite. Based on the data, we know that the longer the immersion process, the higher the bending resistance. The maximum value in this test is obtained during the longest immersion, which is 6 hours. There is a difference in the increase in bending strength when the immersion time is prolonged. The increase in immersion from two hours to four hours increased by 10%, while increasing the soaking time from 4 hours to 6 hours increased by 25%. The cause of difference in bending resistance results can occur because the longer the immersion process causes the fibers to become cleaner and free from impurities. These impurities cause a low bond between the fiber and the matrix. Figure 3 shows that the most prolonged soaked, 6 hours, had the highest flexural strength value. As well as creating rough surface structure. The composite's flexure strength is improved because, at these particular compositions, the EPOFB fiber can effectively transfer the load from the matrix as reported from another discussion [11]. The results of this flexure strength are confirmed by the appearance of the specimen fracture as shown in figure 4.

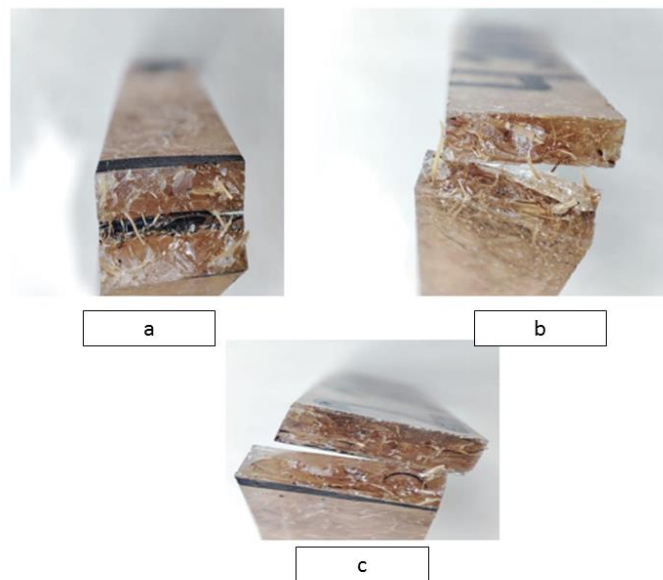


FIGURE 4. fracture of the specimens during testing. a) 2 hours immersion time . b) 4 hours immersion time, c) 6 hours immersion time

Figure 4 shows the fracture cross-section after the bending data collection process. It can be seen that there are more fibers detached from the composite in Figure 4a than in the other names. The detachment of natural fibers from the matrix shows that the bond between the fibers and the matrix is weaker so that the fibers do not break but only detach from the matrix. The small amount of loose fiber in Figure 4c explains the high bending value, where the fiber's applied mechanical force is received by the fiber and causes the fiber to break. Cross sections provide information, with fewer visible fibers indicating a stronger bond between the fibers and the matrix

Tensile Strength

The result of the tensile strength of the composite reinforcement by OPEFB fiber shown at figure 5. From the tensile test data, we can see an increase in the tensile strength value of the composites along with the addition of immersion time.

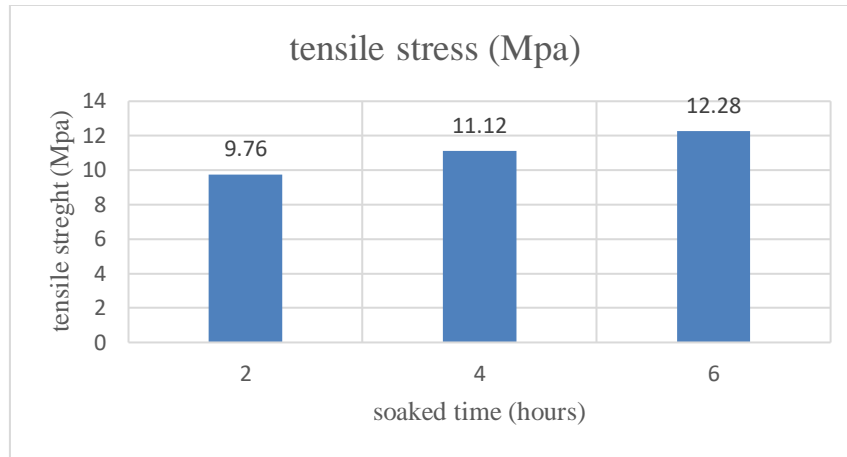


FIGURE 5. Tensile strenght of composite reinforcement OPEFB fiber

This figure shows that there is an increase in tensile strength when the immersion time is extended. The increase in tensile stress from 2 hours to 4 hours of immersion was 12.2%, while the gain between 4 and 6 hours was 9.4%. This increase in tensile strength is due to the rough surface structure due to the effect of the more extended alkali treatment. Alkali increases the pores of fiber, it makes bonding between fiber as reinforcement and resin as matrix increasing [12]. This is confirmed by the appearance of a broken shown at figure 4 below:

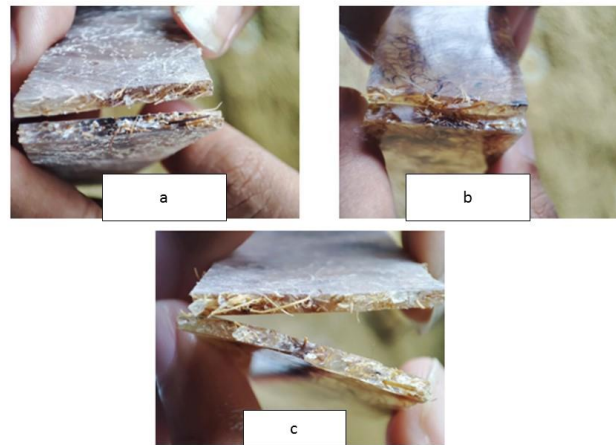


FIGURE 6. fracture of specimen during tensile testing a) 2 hours immersion time . b) 4 hours immersion time, c) 6 hours immersion time

Figure 6 shows the fracture of the specimen tested for bending. Figure 6a shows a worse bond compared to Figures 6b and 6c, and this is because the bond between the fibers and the matrix in Figure 6c is better than the others. Good bonding is affected by the surface roughness of the fibers immersed longer.

CONCLUSION

Alkali treatment of OPEFB fiber varied in time 2, 4, and 6 hours with the aim to determine the effect of soaking time on the mechanical strength of the composite. Composites are made using the hand layup method. The results

show that the longer the soaking time in the pretreatment process will increase the tensile and bending strength of the composite. This is because the bond between the resin as a matrix and OPEFB fibers as a composite reinforcement is getting better. The rougher surface of the OPEFB fiber after soaking makes the bond between the resin and OPEFB fiber better. For further research, it is necessary to carry out a long time variation to determine the maximum time limit for immersion before the fiber is damaged by soaking with alkali.

ACKNOWLEDGDE

This research was supported by funding from RisetMu at the PP Muhammadiyah Diktilitbang. Therefore we would like to thank the PP Muhammadiyah Diktilitbang Council for their support.

REFERENCES

- [1] N. S. Binti Mohd Hafidz, M. S. bin Mohamed Rehan, and H. Binti Mokhtar, "Effect of alkaline treatment on water absorption and thickness swelling of natural fibre reinforced unsaturated polyester composites," in *Materials Today: Proceedings*, 2021, vol. 48, pp. 720–727. doi: 10.1016/j.matpr.2021.02.209.
- [2] N. Zhang, H. Ye, D. Pan, and Y. Zhang, "Effects of alkali-treated kenaf fiber on environmentally friendly geopolymer-kenaf composites: Black liquid as the regenerated activator of the geopolymer," *Constr Build Mater*, vol. 297, Aug. 2021, doi: 10.1016/j.conbuildmat.2021.123787.
- [3] N. A. Latip, A. H. Sofian, M. F. Ali, S. N. Ismail, and D. M. N. D. Idris, "Structural and morphological studies on alkaline pre-treatment of oil palm empty fruit bunch (OPEFB) fiber for composite production," 2019. [Online]. Available: www.sciencedirect.com/www.materialstoday.com/proceedings2214-7853
- [4] Diharjo, K. Pengaruh Perlakuan Alkali terhadap Sifat Tarik Bahan Komposit Serat Rami-Polyester. (2006). *Jurnal Teknik Mesin*, 8(1), 8–13.
- [5] Maryanti, B., & Sidabutar, S. N. S. Pengaruh Waktu Perendaman Serat dalam Larutan Alkali terhadap Kekuatan Impak Komposit Serat Tebu. (2021). *Jurnal Mekanik Terapan Teknik Dan Terbarukan Energi*, 1(2), 42–45.
- [6] Maulana, I. Pengaruh Lama Perendaman Larutan KOH Terhadap Kekuatan Tarik dan Kekuatan Bending Komposit Hibrid Serat Rami dan Bambu. (2021). *Jurnal Teknik Mesin*, 09(03), 99–104.
- [7] Adoe, D. G. H., Pell, Y. M., Studi, P., & Mesin, T. Analisis Pengaruh Perlakuan Alkali Terhadap Wettability Serat Tunggal Widuri. (2021). *Jurnal Teknik Mesin Undana*, 08(02), 23–28.
- [8] Shahril, S. M., Ridzuan, M. J. M., Majid, M. S. A., Bariah, A. M. N., Rahman, M. T. A., & Narayanasamy, P. Alkali treatment influence on cellulosic fiber from *Furcraea foetida* leaves as potential reinforcement of polymeric composites.(2022).. *Jurnal Riset Dan Teknologi Material*, 19(1),
- [9] Ridzuan, M. J. M., Majid, M. S. A., Afendi, M., Azduwin, K., Kanafiah, S. N. A., & Dan-mallam, Y. Efek Dari Paparan Perendaman Perawatan Alkali Pada Kekuatan Tarik Serat Napier. (2015). *Prosedur Manufaktur*, 2(2), 353–358. <https://doi.org/10.1016/j.promfg.2015.07.062>
- [10] A. D. Aguilar *et al.*, "Characterization dataset of oil palm empty fruit bunch (OPEFB) fibers – Natural reinforcement/filler for materials development," *Data Brief*, vol. 45, p. 108618, Dec. 2022, doi: 10.1016/j.dib.2022.108618.
- [11] K. Sakthi Vadivel and P. Govindasamy, "Mechanical and water absorption properties of Acacia Arabica bark fiber/polyester composites: Effect of alkali treatment and fiber volume fraction," in *Materials Today: Proceedings*, 2021, vol. 46, pp. 2281–2287. doi: 10.1016/j.matpr.2021.04.057.
- [12] M. S. Sreekala, M. G. Kumaran, and S. Thomas, "Oil Palm Fibers: Morphology, Chemical Composition, Surface Modification, and Mechanical Properties," John Wiley & Sons, Inc, 1997.

Link Publish : <https://www.atlantis-press.com/proceedings/mest-22/125985971>

176

by Agus Mujianto

Submission date: 10-Dec-2022 07:49PM (UTC+0700)

Submission ID: 1977291207

File name: Agus_Mujianto_176.pdf (487.82K)

Word count: 2481

Character count: 12786

ORIGINALITY REPORT

| | | | |
|------------------|------------------|--------------|----------------|
| 11% | 7% | 7% | 0% |
| SIMILARITY INDEX | INTERNET SOURCES | PUBLICATIONS | STUDENT PAPERS |

PRIMARY SOURCES

| | | |
|---|--|----|
| 1 | Khashayar Khanlari, Maziar Ramezani, Muhammad Hayat, Kelly Piaras, Peng Cao, Thomas Neitzert. "Microstructural and Mechanical Properties of Porous 60NiTi Prepared by Conventional Press-and-sinter Method", MATEC Web of Conferences, 2017 Publication | 1% |
| 2 | K. Sakthi vadivel, P. Govindasamy. "Mechanical and water absorption properties of Acacia Arabica bark fiber/polyester composites: Effect of alkali treatment and fiber volume fraction", Materials Today: Proceedings, 2021 Publication | 1% |
| 3 | digilib.unimed.ac.id Internet Source | 1% |
| 4 | www.mdpi.com Internet Source | 1% |
| 5 | civense.ub.ac.id Internet Source | 1% |

| | | |
|----|--|------|
| 6 | www.pertanika.upm.edu.my Internet Source | 1 % |
| 7 | ebin.pub Internet Source | 1 % |
| 8 | biointerfaceresearch.com Internet Source | <1 % |
| 9 | www.researchsquare.com Internet Source | <1 % |
| 10 | Dominick Wong, Mahmood Anwar, Sujan Debnath, Abdul Hamid, Sudin Izman, A.K. Basak, Alokesh Pramani. "Tensile Strength and Morphological Behavior of Treated Oil Pam Empty Fruit Bunch Particle Reinforced Polymeric Composite", Materials Science Forum, 2022 Publication | <1 % |
| 11 | S.M. Shahril, M.J.M. Ridzuan, M.S. Abdul Majid, A.M.N. Bariah, M.T.A. Rahman, P. Narayanasamy. "Alkali treatment influence on cellulosic fiber from Furcraea foetida leaves as potential reinforcement of polymeric composites", Journal of Materials Research and Technology, 2022 Publication | <1 % |
| 12 | www.neliti.com Internet Source | <1 % |

| | | |
|----|---|------|
| 13 | www.scielo.br Internet Source | <1 % |
| 14 | Bulat M. Galeyev. "Evolution of Gravitational Synesthesia in Music: To Color and Light!", Leonardo, 2003 Publication | <1 % |
| 15 | Shweta Singh, Pankaj Kumar Gupta. "Effect of fiber orientation on mechanical properties of jute/carbon/glass hybrid composite", Materials Today: Proceedings, 2022 Publication | <1 % |
| 16 | garuda.kemdikbud.go.id Internet Source | <1 % |
| 17 | libmast.utm.my Internet Source | <1 % |
| 18 | Nani Nurul Fatihah, Gunawan Ariyanto, Asslia Johar Latipah, Dwi Murdaningsih Pangestuty. "Face Recognition Using Local Binary Pattern and Nearest Neighbour Classification", 2018 International Symposium on Advanced Intelligent Informatics (SAIN), 2018 Publication | <1 % |
| 19 | Panugalla Rama Rao, G. Ramakrishna. "Oil palm empty fruit bunch fiber: surface morphology, treatment, and suitability as reinforcement in cement composites- A state of the art review", Cleaner Materials, 2022 | <1 % |



UMS

Faculty of Engineering
Universitas Muhammadiyah Surakarta

CERTIFICATE

This certificate is awarded for his/her achievement to/as

Febry Adytama

PRESENTER
in the event of

The 9th International Conference on engineering, Technology, and Industrial Application
ICETTIA 2022

Surakarta - Indonesia, 13th-14th December 2022

Dean of Faculty of Engineering

Universitas Muhammadiyah Surakarta



Assoc. Prof. Rois Fatonni, S.T., M.Sc., Ph.D

The 9th ICETTIA 2022 Conference Chair



ICETTIA 2022

Dr. Agung Sugiharto, S.T., M.Eng.



The 9th International Conference on engineering, Technology, and Industrial Application

ICETIA²⁰²²

Faculty of Engineering
Universitas Muhammadiyah Surakarta
Jl. A. Yani Pabelan Kartasura Surakarta 57102
Telp. (0271) 717417 Ext. 3253 Fax. (0271) 715448
Website: <https://icetia.ums.ac.id> | email: icetia@ums.ac.id

Acceptance of Full Paper

No: 589.176/A.6-V/FT/XII/2022

Dear Agus Mujiyanto, Asslia Johar Latipah, Hery Tri Waloyo

We would like to inform the status of your paper for the International Conference on Engineering Technology and Industrial Application (9th ICETIA 2022) with these following details:

| | |
|-------------|--|
| Paper ID | 176 |
| Paper Title | Effect of Fiber Soaking Time on Alkaline Treatment to the Mechanical Strength of the Composite Reinforced Oil Palm Empty Fruit Bunches (OPEFB) Fibers |
| Status | Accepted for oral presentation |
| Publication | Scopus-indexed conference proceeding |

Kindly refer to these following notes:

- Details review process might have been in progress. Please login to your account on the submission website to see the detail review result and update from the reviewers: <http://icetia.ums.ac.id/submit>
- The final manuscript revision should be submitted to the submission system not later than **December 10th 2022**
- There will be no standalone ICETIA 2022 papers since all revised and accepted papers will be published in a Scopus-indexed Conference Proceeding or journals.
- At this stage, kindly make sure that the article follows AIP format. Only selected papers will need to be reformatted according to journals requirement. The decision whether the article would be promoted to be published in the journals will be informed later.
- Authors should register online and make the payment for registration not later than **December 7th 2022**. All presenters need to register as a participant in order to receive a presenter or participant certificate.
- After you have registered online, the payment can be sent to:
 - Name of Bank: BANK NEGARA INDONESIA - (code: 009)
 - Account Number: 0833074464
 - Name of Account Holder: Fakultas Teknik UMS
 - Swift Code: BNINIDJAXXX
- Applicants then should submit the proof of payment by filling the form here: <https://bit.ly/IcetiaPayment2022>
- In addition, for registered participant of ICETIA IX/RAPI XXI, Engineering Faculty of Universitas Muhammadiyah, also will be hosted a **Short Course on "INTRODUCTION TO SAFETY SOFTWARE: EFFECTS AND RISK CURVES"** at **December 14th 2022, 9-12 am**. Registrasion Link : <https://forms.gle/PuAmX87rgC4jpaPy7>. Detailed information on this event is included in the flyer, as attached with this letter.
- For further information, please visit the conference website at <http://icetia.ums.ac.id/2022/>. If you wish to obtain more information, you may also contact the Conference Committee by phone (+62 271 717417 ext. 3253) or email (icetia@ums.ac.id). We look forward to welcoming you on the conference.

Surakarta, 2nd December 2022

Dr. Agung Sugianto
Chair of 9th ICETIA 2022